

D432003



OFFICE OF NAVAL RESEARCH

Contract Nonr 3395(00)

Task No. NR 356-431

3/2/81  
C. L. G.


TECHNICAL REPORT NO. 28

Special Report on the Current Status of the  
Tensile Strength of SiB-2 Elastomers at  
Elevated Temperatures

Compiled by

H. A. Schroeder

19951109 063

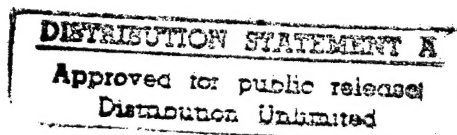

Olin Mathieson Chemical Corporation

Chemicals Division  
New Haven, Connecticut

May 1965

DTIC QUALITY INSPECTED 8

Reproduction in whole or in part is permitted for any purpose of  
the United States Government

DEPARTMENT OF DEFENSE  
PLASTICS TECHNICAL EVALUATION CENTER  
PICATINNY ARSENAL, DOVER, N. J.

PLASTIC 2171  
-28

Alt-Z FOR HELP3 ANSI

3 HDX 3

3 LOG CLOSED 3 PRINT OFF 3 PARITY

\*MSG DIA DROLS PROCESSING-LAST INPUT IGNORED

-- 1 OF 1

\*\*\*DTIC DOES NOT HAVE THIS ITEM\*\*\*

-- 1 - AD NUMBER: D432003

-- 5 - CORPORATE AUTHOR: OLIN MATHIESON CHEMICAL CORP NEW HAVEN CONN

-- 6 - UNCLASSIFIED TITLE: SPECIAL REPORT ON THE CURRENT STATUS OF THE

-- TENSILE STRENGTH OF SIB-2 ELASTOMERS AT ELEVATED TEMPERATURES,

--10 - PERSONAL AUTHORS: SCHROEDER, H. A. ;

--11 - REPORT DATE: MAY , 1965

--12 - PAGINATION: 12P

--14 - REPORT NUMBER: TR-28

--15 - CONTRACT NUMBER: NONR339500

--20 - REPORT CLASSIFICATION: UNCLASSIFIED

--21 - SUPPLEMENTARY NOTE: SEE ALSO PL-36263 - PL-36269.

--22 - LIMITATIONS (ALPHA): APPROVED FOR PUBLIC RELEASE; DISTRIBUTION

-- UNLIMITED. AVAILABILITY: OLIN CHEMICALS, 120 LONG RIDGE RD,

-- STAMFORD, CT. 06904.

--33 - LIMITATION CODES: 1 24

-- END

Y FOR NEXT ACCESSION

END

Alt-Z FOR HELP3 ANSI

3 HDX 3

3 LOG CLOSED 3 PRINT OFF 3 PARITY

# Special Report on the Current Status of the Tensile Strength of SiB-2 Elastomers at Elevated Temperatures

Compiled by H. A. Schroeder

Accession For	
NTIS CRA&I	✓
DTIC TAB	
Unannounced	
Justification	
By <b>ADD 432023</b>	
Distribution /	
Availability Code	
Dist	Avail and/or Special
<b>A-1</b>	

## Summary


[ Modified SiB-2 rubbers can now be routinely compounded and pressure molded to provide an elastomer having a tensile strength of 450 psi. at ambient temperatures. On testing at 600°F, these specimens retain a tensile strength of 30-35%, or up to 45% by the addition of Fe<sub>2</sub>O<sub>3</sub> as an antioxidant. At 800°F, 10% (and in certain instances 15%) retention was observed. These retention data surpass those reported for silicones and also are better than the corresponding values for Viton B.

*6 tables, 2 appendices. (A.m.)*

## Introduction

The advent of the missile age and the development of supersonic jet aircraft has produced an increasing demand for nonmetallic materials which can be used at high temperatures. Of special importance is the synthesis of thermally stable elastomers superior to those presently available. Various requirements for them exist and more are projected for use in Mach 3 airplanes. Typical examples for their application are pneumatic seals for doors and windows, interlaminar layers for glass windshields, and integral fuel tank sealants, among many others. Each of these requires outstanding thermal stability beside individual properties which are specifically suited to the desired function.


During the past year we have discovered under this contract<sup>1</sup> a new family of boron-containing elastomers which show promise of satisfactory performance under extreme conditions. From among these, we have selected as the most attractive candidate for elevated temperature capability "SiB-2", a polydimethylsiloxane containing m-carborane nuclei in regular intervals in the skeleton.

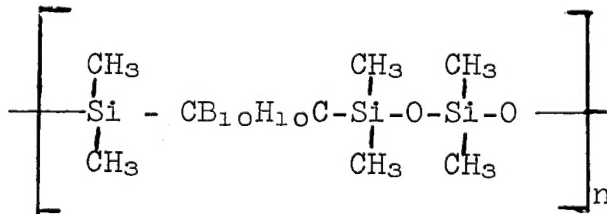

<sup>1</sup> Olin Mathieson Chemical Corporation, various Monthly Progress Reports for Contract Nonr 3395(00).

In this polymer, the ratio of thermostabilizing carboranylene and flexibility producing dimethylsiloxo groups appears to be in the right balance as to assure maximum advantage of both properties.

Since "plain" SiB-2 requires up to 5% of peroxide for effective curing, we subsequently synthesized so-called "modified" SiB-2 rubbers by introduction of a minimal amount of unsaturated groups by introduction of a minimal amount of unsaturated groups as additional curing sites.<sup>2</sup> In the example as illustrated, part of the methyl groups are replaced by vinyl groups. Other modifications investigated in place of vinyl are allyl and vinyl-o-carboranyl, which all permit a peroxide decrease to 2%.

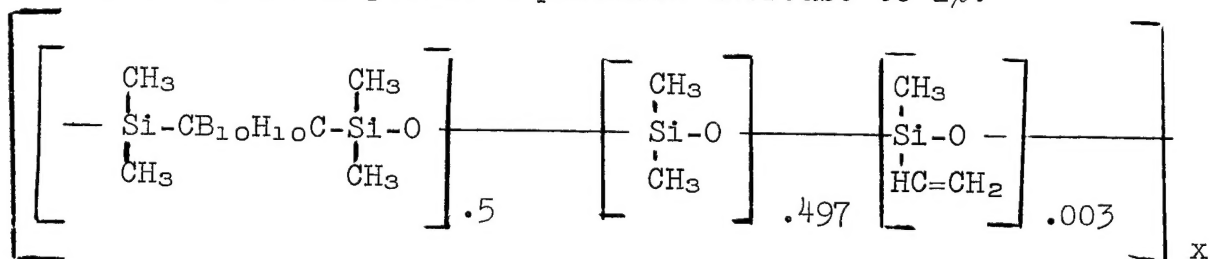

The present program<sup>3</sup> concerns the development of this and other elastomeric systems. Since we are only at the outset of this study and our previous work has given us only indications of what that rubber may do, an extensive although exploratory testing at elevated temperatures seemed necessary to gain enough data which would allow us to pursue our work along specific guide lines.

#### Test Material Preparation

To obtain a set of lucid data, a number of parameters involved in the sample preparation were kept constant. The use of various fillers had been scanned previously and we had found finely divided silica to be most suitable in regard to tensile strength and elongation; the commercial product selected was "Cab-O-Sil". As the free radical type curing agent, "Di-Cup 40", in 2 parts concentration, was used in almost every instance. The process of pressure molding as well as the curing cycle were identical for all samples. The proportion of unsaturated groups in modified SiB-2 rubbers always corresponded to the formula of vinyl modified SiB-2 illustrated in the introduction.

The cured SiB-2 test specimens were all prepared as follows: Purified and dried SiB-2 (plain or modified) rubber was milled to a crepe on a cold, 5 in. mill; the desired amounts of solid filler (Cab-O-Sil), curing agent (Di-Cup 40) and, in some cases Fe<sub>2</sub>O<sub>3</sub> or Al(OH)<sub>3</sub> as an antioxidant, were thoroughly blended and then milled into the crepe. Enough compounded rubber was placed in a 2" x 5" mold to give a final specimen of ~1/8" thickness; these specimens

<sup>2</sup> Olin Mathieson Chemical Corporation, Technical Report No. 26 for Contract Nonr 3395(00) by S. Papetti, B. B. Schaeffer, A. P. Gray and T. L. Heying, in preparation.

<sup>3</sup> Contract NObs-92143, Project Serial No. SR007-03-03, Task 1000

were cured at 311°F at either 375 or 500 psig. After cooling, the specimens were removed and post-cured in air at 212°F for 24 hours, 302°F for 24 hours and finally 392°F for 48 hours.

### Test Procedure

Ambient temperature tensile testing is done in the normal manner on an Instron Testing Apparatus, Model TT-CM1 using a crosshead speed of 2"/min. For elevated temperature testing, the sample and holders are suspended in a Missimers Inc., Temperature Test Chamber, Model TFU 3.2\_100x 1000; the chamber is brought to the selected temperature equilibrium, the box is opened and the dogbone is positioned and the door closed. The box is allowed to return to temperature, allowed to remain for 5 minutes (total time ~15 min.) and then pulled.

### Results and Discussion

Since the SiB elastomers are basically polydimethylsiloxanes, it seems appropriate to compare them first of all with the silicones, and also to apply as much as possible the latter's established technology for improving the SiB polymers. The room temperature tensile strengths of commercial silicone rubbers generally fall in the 300 - 700 psi. range although some specialty types may be as high as 1000-1200 psi.

Our first objective was to try to improve the ambient temperature tensile strengths while maintaining adequate elongation. In this respect, modified SiB-2 polymers were found to be definitely superior to plain SiB-2.

Table 1<sup>a</sup> reflects the effect of the various modifications (as compared to our standard unmodified SiB-2) on room temperature tensile strength at low loading.

TABLE I  
Tensile Strength and Elongation:  
Effect of Modification at Low Filler Content

<u>Modification</u>	<u>SiO<sub>2</sub> parts</u>	<u>Shore Hardness (A)</u>	<u>Elongation %</u>	<u>Tensile psi.</u>
None	25	68	55	201
Vinyl	20	58	61	192
CH=CH <sub>2</sub>	25	57	125	277
CH=CH <sub>2</sub>	30	57	87	215
CH=CH <sub>2</sub>	35	64	92	279
Allyl	25	72	115	384
Allyl	25	72	136	446
Allyl	35	73	140	375

<sup>a</sup> Tables I-VI which appear in this discussion are organizations of properly selected data which serve to illustrate certain points or establish trends. A complete tabulation of all meaningful evaluation data obtained in two tables in the Appendix.

It should be pointed out that at present we are not so much concerned with absolute numerical values as we are in establishing trends and effects on these values. Simple vinyl modification was ineffective. Vincylcarboranyl modification showed measurable improvement while allyl modification, as expected, gave the highest tensile and elongation values. (This is typical of allyl modified silicones in general.) The effect of variation of parts of silica in the 25-75 ranges seems negligible; when 50 or more parts of silica are used the effect becomes pronounced as can be seen in Table II.

TABLE II

Tensile Strength and Elongation:

Effect of Modification at High Filler Content

<u>Modification</u>	<u>SiO<sub>2</sub> parts</u>	<u>Shore Hardness</u>	<u>Elongation %</u>	<u>Tensile psi.</u>
Vinyl	50	71	72	333
Vinyl	50	67	88	372
Vinyl	50	80	53	430
Vinyl	60	78	49	495
Vinyl	75	85	18	503
CH=CH <sub>2</sub>	50	70	54	331
CH-CH <sub>2</sub>	50	72	67	341
CH=CH <sub>2</sub>	50	74	70	459
Allyl	50	66	78	312
Allyl	50	75	102	413
Allyl	60	74	37.5	319
Allyl	75	78	39	351

Note here that at room temperature additional filler markedly raised the tensile strengths of both the vinyl and vinylcarboranyl modifications while there is no effect on the allyl modified polymer. Sixty parts of silica appears to be the maximum which can be tolerated without causing a sharp decline in elongation.

A real test of an elastomer for use at high temperature is the measurement of the percentage of retention of a given physical property at these temperatures. Table III therefore summarizes the performance of certain samples (low loading) discussed above at 600 and 800°F.

TABLE III

Tensile Strength and Elongation:  
Effect of Modification at High Temperatures (Low Filler Content)

<u>Modification</u>	<u>SiO<sub>2</sub> parts</u>	<u>Ambient</u>		<u>600°F</u>			<u>800°F</u>		
		<u>Elong. %</u>	<u>Tensile psi.</u>	<u>Elong. %</u>	<u>Tensile psi.</u>	<u>Retention % psi.</u>	<u>Elong. %</u>	<u>Tensile psi.</u>	<u>Retention % psi.</u>
none	25	55	201	40	62	30.8	11	33	16.4
$\Theta\text{CH}=\text{CH}_2$	25	109	239	72.6	73.4	30.7	22	18.2	7.6
$\Theta\text{CH}=\text{CH}_2$	25	125	277	90	89	32.1	_____		
$\Theta\text{CH}=\text{CH}_2$	35	92	279	70	86.6	31	_____		
allyl	25	115	384	92	96.5	18.1	_____		
allyl	25	136	446	66	33.3	7.5		13.1	2.9
allyl	35	140	375	156	69.5	18.5	33	10.9	2.9

Although at 25 parts silica the allyl modified SiB-2 showed by far the highest room temperature tensile strength, at 600 and 800°F it is considerably inferior to both vinylcarboranyl modified and unmodified SiB-2. Note the retention of ~30% of tensile strength of the latter two at 600°F.

Table IV illustrates a similar treatment of the more highly filled specimens.

TABLE IV

Tensile Strength and Elongation:

Effect of Modification at High Temperatures (High Filler Content)

<u>Modification</u>	<u>SiO<sub>2</sub> parts</u>	<u>Ambient</u>		<u>600°F</u>			<u>800°F</u>		
		<u>Elong. %</u>	<u>Tensile psi.</u>	<u>Elong. %</u>	<u>Tensile psi.</u>	<u>Retention % psi.</u>	<u>Elong. %</u>	<u>Tensile psi.</u>	<u>Retention % psi.</u>
vinyl	50	72	333	45	122	36.6	15	26.5	8
vinyl	50	53	430	67.5	123.5	29	11	21.5	5
vinyl	60	49	495	54.6	158	32			
vinyl	75	18	503				—	26.8	5.3
$\Theta\text{CH}=\text{CH}_2$	50	67	341	77.5	120.9	35.4	19.2	22	6.4
$\Theta\text{CH}=\text{CH}_2$	50	70	459	50	187.5	40.8	25	43.4	9.4
allyl	50	102	413	58	91.5	22.3	22	25.6	6.2

These results shows that again the allyl modification is inferior to either the vinyl or vinylcarboranyl types. Samples of each of the latter two retained more than 30 percent of their tensile strength at 600°F and 5-8% and 6-9% respectively at 800°F. We also point out that visual observance of the specimens during test made it obvious that the allyl materials was softening and deforming while the others generally retained their structural identity.

These results have led us to drop from further consideration the use of allyl modified SiB-2 for high temperature evaluation. This also points out the principal that the variation which shows the best room temperature properties need not necessarily perform as well at elevated temperature as another very similar material; it is the old story of the 'weakest link in the chain'.



During these and earlier studies<sup>2</sup> it had become apparent to us that initial deterioration of an elastomer sample at elevated temperatures could be observed as a surface hardening and/or cracking while the interior of the sample was quite unchanged. Such a happening could be the start of a failure in a tensile test. We have every reason to suspect oxidative attack and have begun to scan potential antioxidants and determine whether they are beneficial. Table V points out the effect of  $\text{Fe}_2\text{O}_3$ , a potential antioxidant on one formulation system, namely the vinylcarboranyl variety with 50 parts Cab-O-Sil. The additive of one part of the  $\text{Fe}_2\text{O}_3$  produced no significant difference in tensile strength retention at either 600 or 800°F; on the other hand the addition of three parts  $\text{Fe}_2\text{O}_3$  gave the highest retention yet observed at 600°F, specifically 45.7% and the retention at 800°F was above 10%. We believe this effect to be real and important and this is an important point for further study.

TABLE V

Tensile Strength and Elongation:

Effect of  $\text{Fe}_2\text{O}_3$  at Various Temperatures

<u>Modifi-</u> <u>cation</u>	<u><math>\text{SiO}_2</math></u> <u>parts</u>	<u>Anti-</u> <u>oxidant</u> <u>(parts)</u>	<u>Ambient</u>		<u>600°F</u>			<u>800°F</u>		
			<u>Elong.</u> <u>%</u>	<u>Tensile</u> <u>psi.</u>	<u>Elong.</u> <u>%</u>	<u>Tensile</u> <u>psi.</u>	<u>Retention</u> <u>% psi.</u>	<u>Elong.</u> <u>%</u>	<u>Tensile</u> <u>psi.</u>	<u>Retention</u> <u>% psi.</u>
$\text{CH}=\text{CH}_2$	50	—	67	341	77.5	120.9	35.4	19.2	22	6.4
$\text{CH}=\text{CH}_2$	50	—	70	459	50	187.5	40.8	25	43.4	9.4
$\text{CH}=\text{CH}_2$	50	$\text{Fe}_2\text{O}_3$ (1)	100	428	61	128	27.5	8	32.8	7.6
$\text{CH}=\text{CH}_2$	50	$\text{Fe}_2\text{O}_3$ (3)	69	357	75	163	45.7	—	38.4	10.7

Other spurious results regarding the trials of the antioxidants are summarized in Table VI; we remind the reader that these studies have only recently begun and are still in progress.

TABLE VI  
Tensile Strength and Elongation:  
Effect of Various Antioxidants at Various Temperatures

Modifi- cation	SiO <sub>2</sub> parts	Anti- oxidant (parts)	Ambient		600°F			800°F		
			Elong. %	Tensile psi.	Elong. %	Tensile psi.	Retention % psi.	Elong. %	Tensile psi.	Retention % psi.
none	25	—	55	201	40	62	30.8	11	33	16.4
none	25	Fe <sub>2</sub> O <sub>3</sub> (0.5)	43	202	37.5	93.3	46.4	—		
CH=CH <sub>2</sub>	25	—	109	239	72.6	73.4	30.7	22	18.2	7.6
CH=CH <sub>2</sub>	25	Fe <sub>2</sub> O <sub>3</sub> (1)	158	244	90	103	42.2	—	28.8	11.8
CH=CH <sub>2</sub>	25	Fe <sub>2</sub> O <sub>3</sub> (3)	182	271	81	100	36.9	11	25.9	9.6
CH=CH <sub>2</sub>	25	Al(OH) <sub>3</sub> (3)	190	226	68	58.5	25.9	—	22.1	10.0
vinyl	25	Al(OH) <sub>3</sub> (3)	160	232	83	77.4	33.3	—	15.2	6.5

These data point out that in general  $\text{Fe}_2\text{O}_3$  aids in retention of strength in general; the effect of hydrous alumina is questionable.<sup>3</sup> The second example using 0.5 parts  $\text{Fe}_2\text{O}_3$  with unmodified SiB-2 showed exceptionally high retention at 600°F; check of the records showed that this sample of  $\text{Fe}_2\text{O}_3$  was from a different source than all others reported and this point is being looked into. Also this particular sample of unmodified SiB-2 in the various formulations in which it was used showed generally better results than we had become accustomed to note. Again careful check of the history of the sample has given us a clue as to why this may have occurred; this is to be examined in more detail.

---

3

Studies elsewhere (Mare Island Naval Shipyard, Rubber Laboratory, Report No. 1-14, 9 November 1964) have shown that hydrous alumina in conjunction with a chloro polymer may be useful. Also the use of antimony oxide (U.S. Rubber Co., Final Report for Contract NObs 84025, March 9, 1962) is suggested elsewhere. We intend to evaluate these as well as many other compounds we suspect could be useful.

### Conclusions

Appropriate studies indicate that vinylcarboranyl (and possibly vinyl) modification (to speed curing) of SiB-2 is preferred over allyl modification for high temperature use.

Increasing the amount of silica, as expected, increases the tensile strength of the elastomers; at loadings >60 parts the elongation drops off markedly.

Retention of 30-45% of tensile strength at 600°F and >10% at 800°F in air has been achieved. The use of iron oxide as an antioxidant assists in this regard.

Further improvements from the study of the effects of such variables as the curing cycle, filler contents, addition of selected antioxidants, etc can be expected.

Comparison of SiB-2 rubber with other elastomers such as Viton and fluorosilicones on aging at ~ 700°F in air will be stressed during the forthcoming period.

Appendix I  
Tensile Strength Determinations at Ambient Temperatures

Sample No.	Modification	SiO <sub>2</sub> parts	Antioxidant (parts)	Peroxide <sup>1</sup> (parts)	Shore A	Elongation %	Tensile psi.	Test Variation (min.-max.)	Number of Samples Tested
92	none	25	Fe <sub>2</sub> O <sub>3</sub> (0.5)	BP (2)	65	43	202	179-230	3
86	vinyl	20	—	BP (1.5)	58	61	192	173-218	4
94-95	vinyl	50	—	DC (2)	71	72	333	301-360	4
122-123	vinyl	50	—	DC (2)	80	53	430	382-454	4
143	vinyl	50	—	DC (2)	67	88	372	353-398	4
144	vinyl	60	—	DC (2)	78	49	495	489-507	4
145	vinyl	75	—	DC (2)	85	18	503	490-516	5
147	vinyl	25	Al (OH) <sub>3</sub> (3)	DC (2)	56	160	232	232-232	2
93	CH=CH <sub>2</sub>	50	—	DC (2)	70	54	331	281-368	3
98-99	CH=CH <sub>2</sub>	50	—	DC (2)	74	70	459	410-492	6
102	CH=CH <sub>2</sub>	25	—	DC (2)	57	125	277	248-308	4
103	CH=CH <sub>2</sub>	30	—	DC (2)	57	87	215	186-242	4
104	CH=CH <sub>2</sub>	35	—	DC (2)	64	92	279	260-317	4
126-127	CH=CH <sub>2</sub>	50	—	DC (2)	72	67	341	325-368	4
128-129	CH=CH <sub>2</sub>	50	Fe <sub>2</sub> O <sub>3</sub> (3)	DC (2)	70	69	357	338-371	4
130-131	CH=CH <sub>2</sub>	50	Fe <sub>2</sub> O <sub>3</sub> (1)	DC (2)	66	100	428	423-432	2
132-133	CH=CH <sub>2</sub>	25	Fe <sub>2</sub> O <sub>3</sub> (3)	DC (2)	55	179	254	218-289	3
134-135	CH=CH <sub>2</sub>	25	Fe <sub>2</sub> O <sub>3</sub> (1)	DC (2)	55	158	244	234-263	4
136-137	CH=CH <sub>2</sub>	25	Fe <sub>2</sub> O <sub>3</sub> (3)	DC (2)	55	182	271	213-298	4
138	CH=CH <sub>2</sub>	34	Al (OH) <sub>3</sub> (3)	DC (2)	58	120	203	180-221	4
146	CH=CH <sub>2</sub>	25	Al (OH) <sub>3</sub> (3)	DC (2)	56	190	226	214-240	3
105	allyl	25	—	DC (2)	72	136	446	427-468	3
106	allyl	25	—	DC (2)	72	115	384	357-426	4
108	allyl	35	—	DC (2)	73	140	375	368-381	2
110-111	allyl	50	—	DC (2)	75	102	413	400-425	2
139	allyl	34	Al (OH) <sub>3</sub> (3)	DC (2)	50	130	183	146-218	4
140	allyl	50	—	DC (2)	66	78	312	290-323	4
141	allyl	60	—	DC (2)	74	37.5	319	297-334	4
142	allyl	75	—	DC (2)	78	39	351	320-364	4

1. See Appendix II for definition.

# Appendix II

Tensile Strength Determinations at Ambient and Elevated Temperatures

Sample No.	Modification	SiO <sub>2</sub> <sup>1</sup> parts	Antioxidant (parts)	Peroxide <sup>2</sup> (parts)	Shore A Hardness	-40°F Tensile psi.	Ambient Elong. % Tensile psi.	600°F Elong. % Tensile psi.	800°F Elong. % Tensile psi.	Retention % psi.
64	none	25	—	BP(2)	68	—	55 201	40 62 30.8	11 33 16.4	—
92	none	25	Fe <sub>2</sub> O <sub>3</sub> (0.5)	BP(2)	65	—	43 202	37.5 93.9 46.4	—	—
147	vinyl	25	Al(OH) <sub>3</sub> (3)	DC(2)	56	—	160 232	83 77.4 33.4	—	15.2 6.5
94-95	vinyl	50	—	DC(2)	71	1370	72 333	45 122 36.6	15 26.5 8	—
122-123	vinyl	50	—	DC(2)	80	1948	53 430	67.5 123.5 29.0	11 21.5 5	—
144	vinyl	60	—	DC(2)	78	—	49 495	54.6 158 32	—	—
145	vinyl	75	—	DC(2)	85	—	18 503	—	—	26.8 5.3
55	CH=CH <sub>2</sub>	25	—	Va(1)	—	—	109 239	72.6 73.4 30.7	22 18.2 7.6	—
102	CH=CH <sub>2</sub>	25	—	DC(2)	57	—	125 277	90 89 32.1	—	—
134-135	CH=CH <sub>2</sub>	25	Fe <sub>2</sub> O <sub>3</sub> (1)	DC(2)	55	—	158 244	90 103 42.2	—	28.8 11.8
132-133	CH=CH <sub>2</sub>	25	Fe <sub>2</sub> O <sub>3</sub> (3)	DC(2)	55	—	179 254	83 79 31.1	—	—
136-137	CH=CH <sub>2</sub>	25	Fe <sub>2</sub> O <sub>3</sub> (3)	DC(2)	55	—	182 271	81 100 36.9	11 25.9 9.6	—
146	CH=CH <sub>2</sub>	25	Al(OH) <sub>3</sub> (3)	DC(2)	58	—	190 226	68 58.5 25.9	—	22.1 10
104	CH=CH <sub>2</sub>	35	—	DC(2)	64	—	92 279	70 86.6 31	—	—
98-99	CH=CH <sub>2</sub>	50	—	DC(2)	74	1394	70 459	50 187.5 40.8	25 43.4 9.4	—
126-127	CH=CH <sub>2</sub>	50	—	DC(2)	72	1288	67 341	77.5 120.9 35.4	19.2 22 6.4	—
130-131	CH=CH <sub>2</sub>	50	Fe <sub>2</sub> O <sub>3</sub> (1)	DC(2)	66	—	100 428	61.5 128 27.5	8 32.8 7.6	—
128-129	CH=CH <sub>2</sub>	50	Fe <sub>2</sub> O <sub>3</sub> (3)	DC(2)	70	—	69 357	75 163 45.7	—	38.4 10.7
105	allyl	25	—	DC(2)	72	—	136 446	66 33.3 7.5	—	13.1 2.9
106	allyl	25	—	DC(2)	72	—	115 384	92 69.5 18.1	—	—
108	allyl	35	—	DC(2)	73	—	140 375	156 69.5 18.5	33 10.9 2.9	—
110-111	allyl	50	—	DC(2)	75	2151	102 413	58 91.5 22.3	22 25.6 6.2	—

<sup>1</sup> SiO<sub>2</sub> : Cab-O-Sil M5 (Cabot Corp.)

<sup>2</sup> Peroxides:

Va - Varox (2,5-bis(tert.-butylperoxy)-2,5-dimethyl hexane.  
BP - Benzoyl Peroxide.  
DC - DI CUP 40 (40% dicumyl peroxide supported on calcium carbonate).

# DISTRIBUTION LIST FOR SPECIAL TECHNICAL REPORTS

Department of the Army Supply & Maintenance Command Maintenance Readiness Division Washington, D. C. Attn: Technical Director (1)	Dr. Albert Lightbody Naval Ordnance Laboratory White Oak, Maryland (1)
U. S. Army Natick Laboratories Clothing & Organic Materials Division Natick, Massachusetts Attn: Associate Director (1)	Commanding Officer and Director U. S. Naval Civil Engineering Lab. Port Hueneme, California Attn: Chemistry Division (1)
Chief, Bureau of Ships Department of the Navy Washington, D. C. Attn: Code 342A (1) Code 634C (1)	Aeronautical System Division ASRCNP Wright-Patterson AFB, Ohio (1)
Chief, Bureau of Naval Weapons Department of the Navy Washington, D. C. Attn: Code RRMA-1 (1)	Plastics Technical Evaluation Center Picatinny Arsenal Dover, New Jersey ✓ (1)
Commanding Officer U. S. Army Electronics Research and Development Laboratory Fort Monmouth, New Jersey 07703 Attn: SELRA/DR (1)	Commander Ordnance Corps Rock Island Arsenal Rock Island, Illinois Attn: ORDEC 9320-ZTO (1)
Naval Radiological Defense Laboratory San Francisco, California 94135 (1)	New York Naval Shipyard Materials Laboratory Brooklyn, New York Attn: Mr. B. Simms (1)
Naval Ordnance Test Station China Lake, California Attn: Head, Chemistry Division (1) Code 40 (1) Code 50 (1)	Director Naval Research Laboratory Washing, D. C. Attn: Mr. J. A. Kies, Code 6210 (1) Mr. E. J. Kohn, Code 6110 (1) Mr. R. B. Fox, Code 6120 (1)
Commanding Officer U. S. Army Chemical Research and Development Laboratories Edgewood Arsenal, Maryland (1)	Naval Ordnance Test Station China Lake, California Attn: Dr. Kaufman, Code 4544 (1) Mr. S. H. Herzog, Code 5577 (1) Mr. R. J. Landry (1)
Dr. C. Haber Naval Ordnance Laboratory Corona, California (1)	
Dr. Porter W. Erickson Chemistry Research Department Non-Metallic Materials Division Naval Ordnance Laboratory White Oak, Silver Spring, Maryland (1)	